

Supporting Information

FeCo alloy nanoparticle encapsulated in hollow N-doped carbon as bifunctional electrocatalyst for aqueous zinc-air batteries with low voltage gap

Nan Li ‡, Ting Yang ‡, Hang Lou, Lijuan Huang, Xiaoyu Ma, Hao Jiang, Jiaxiang Xiao, Chao Xie, Yahui Yang**

College of Chemistry and Chemical Engineering, Hunan Normal University, Changsha 410081, China

‡These authors contributed equally to this work and should be considered as co-first authors.

*Corresponding author

E-mail address: xc9229@outlook.com (C. Xie); yangyahui2002@sina.com (Y. Yang)

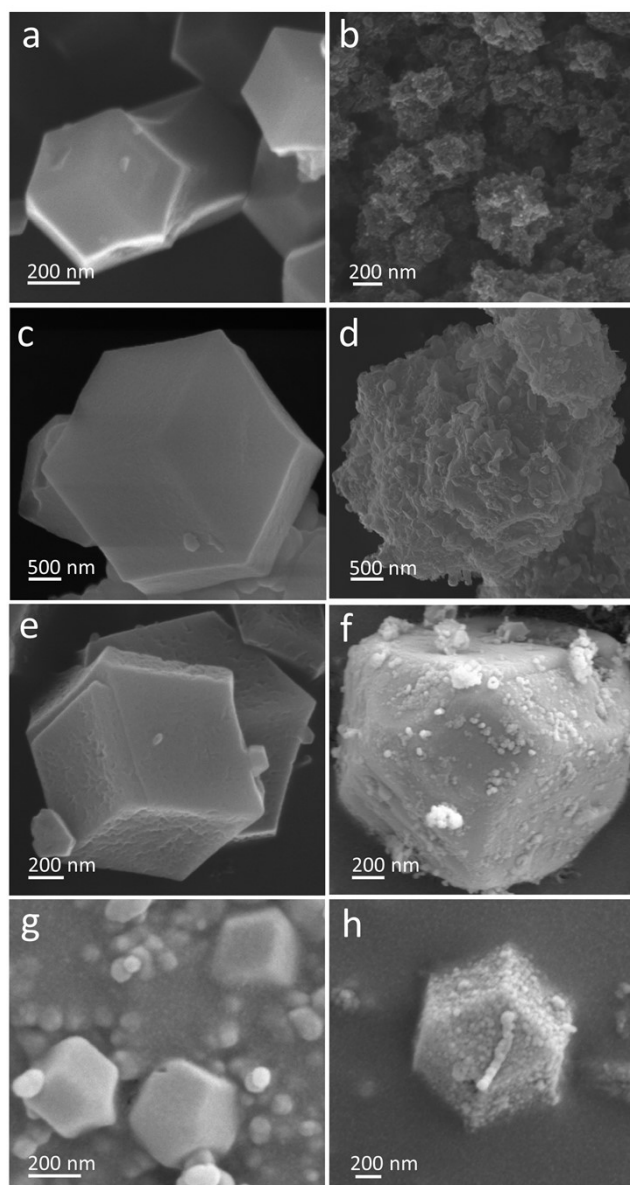


Figure S1. SEM images of (a) ZnFe-ZIF-0.1, (b) $\text{Fe}_x\text{Co}_y\text{@N-C-0.1}$, (c) ZnFe-ZIF-0.5, (d) $\text{Fe}_x\text{Co}_y\text{@N-C-0.5}$, (e) ZnFe-ZIF-0.3, (f) Fe@N-C, (g) ZnCo-ZIF, and (h) Co@N-C.

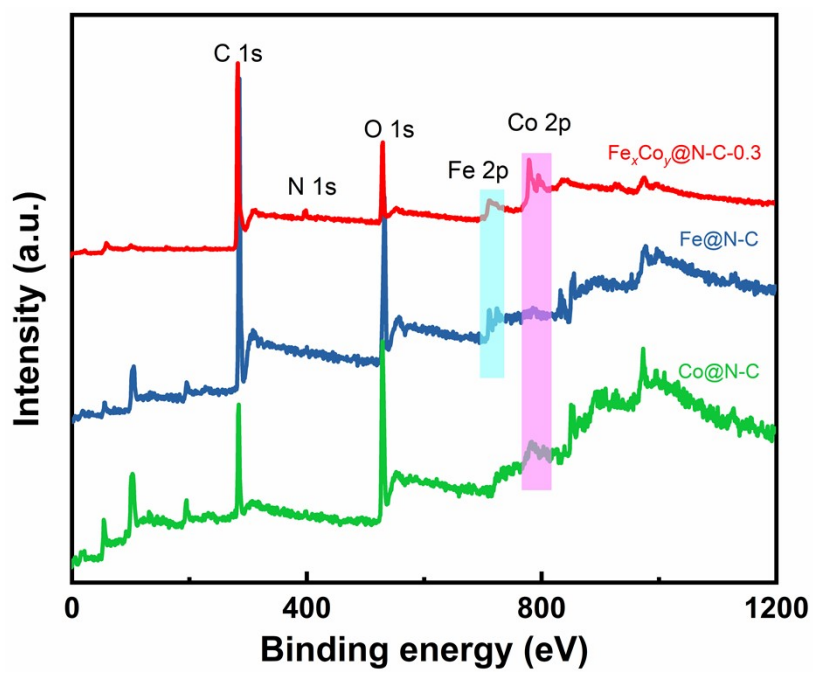


Figure S2. XPS spectrums of $\text{Fe}_x\text{Co}_y@N-C-0.3$, $\text{Fe}@N-C$ and $\text{Co}@N-C$.

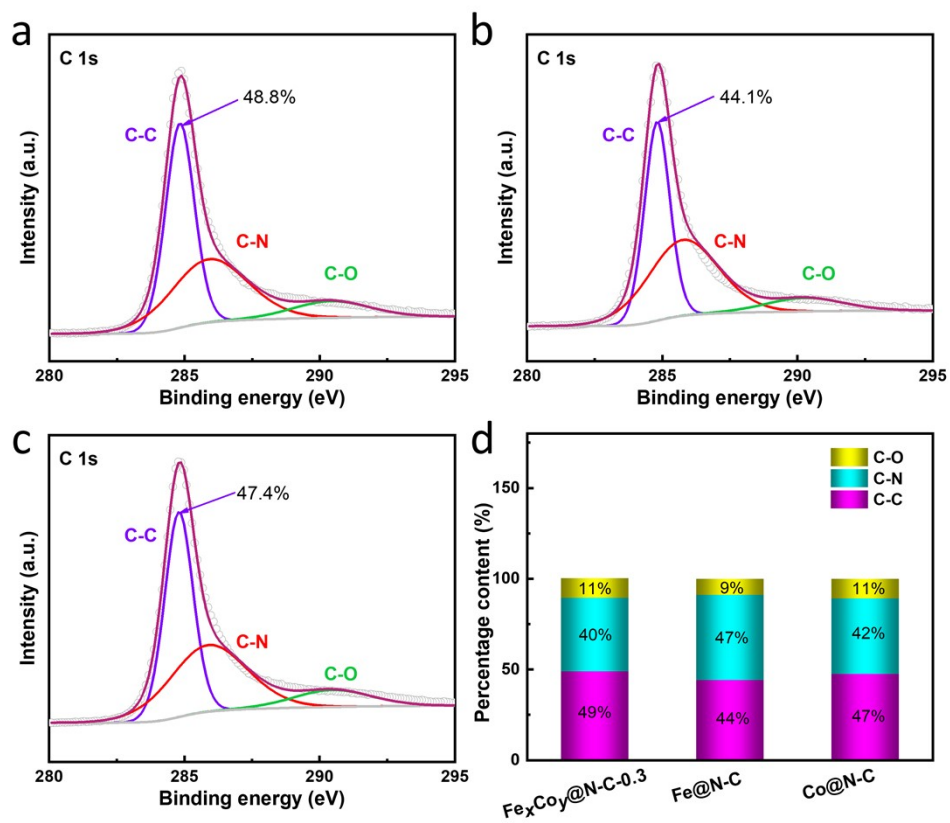


Figure S3. The C 1s XPS spectrums of (a) $\text{Fe}_x\text{Co}_y@N-C-0.3$, (b) $\text{Fe}@N-C$, and (c) $\text{Co}@N-C$. (d) Comparison of various C contents in $\text{Fe}_x\text{Co}_y@N-C-0.3$, $\text{Fe}@N-C$, and $\text{Co}@N-C$.

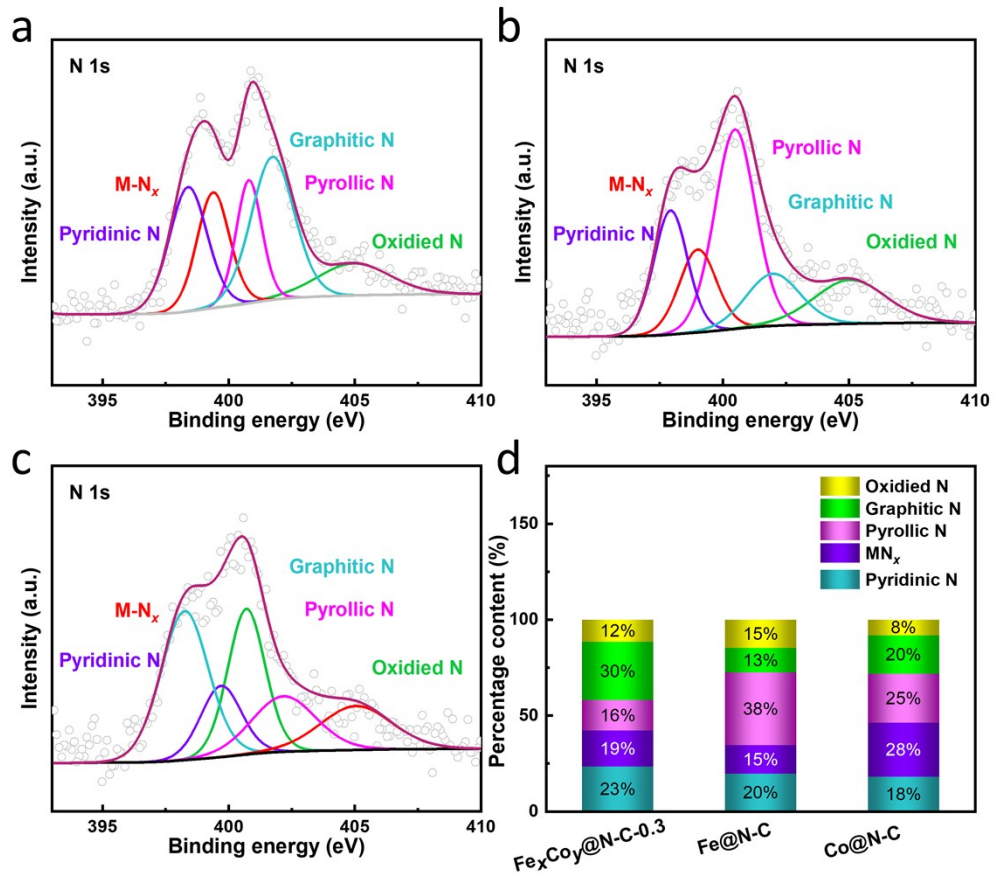


Figure S4. The N 1s XPS spectra of (a) Fe_xCo_y@N-C-0.3, (b) Fe@N-C, and (c) Co@N-C. (d) Comparison of various N contents in Fe_xCo_y@N-C-0.3, Fe@N-C, and Co@N-C.

Table S1. Comparison of the ORR performance of as-prepared catalysts.

| Catalyst | $E_{1/2}$ (V vs. RHE) | The Tafel slope (mV dec ⁻¹) |
|---|-----------------------|---|
| Fe _x Co _y @N-C-0.1 | 0.839 | 90.9 |
| Fe_xCo_y@N-C-0.3 | 0.842 | 88.1 |
| Fe _x Co _y @N-C-0.5 | 0.836 | 94.3 |
| Fe@N-C | 0.810 | 101.5 |
| Co@N-C | 0.803 | 118.2 |
| Pt/C | 0.809 | 100.7 |

Table S2. Comparison of ORR performance (vs. RHE) of Fe_xCo_y@N-C-0.3 with reported M-N-C catalysts in alkaline solution.

| Catalysts | $E_{1/2}$ (V) | E_{onset} (V) | Ref. |
|---|---------------|-----------------|--|
| Fe_xCo_y@N-C-0.3 | 0.842 | 0.98 | This work |
| Fe ₈ Co _{0.2} -NC-800 | 0.820 | / | <i>Nano-Micro Lett.</i> 2023 , 15, 26. |
| NP-Co _{SA} NC | 0.860 | / | <i>Energy Storage Materials</i> 2023 , 56, 165–173. |
| CoFe@NC/KB-800 | 0.845 | 0.95 | <i>Chem. Eng. J.</i> 2022 , 427, 131614. |
| CoNi-CoN ₄ -HPC-900 | 0.820 | 1.03 | <i>Nano Energy</i> 2022 , 99, 107325. |
| ZnCo-HNC | 0.820 | 1.05 | <i>Small</i> 2022 , 18, e2107141. |
| Co@NPC/C-MWCNTs | 0.790 | 0.87 | <i>Chem. Eng. J.</i> 2022 , 432, 134192. |
| CoNP@FeNC-0.05 | 0.850 | 1.02 | <i>Nano-Micro Lett.</i> 2022 , 14, 162. |
| CoFe/S-N-C | 0.855 | / | <i>Chem. Eng. J.</i> 2022 , 429, 132174. |
| Co/CoFe@NC | 0.840 | 0.97 | <i>Nano-Micro Lett.</i> 2021 , 13, 126. |
| FeCo/N-HCSs | 0.791 | 0.98 | <i>Chem. Eng. J.</i> 2021 , 407, 127961. |
| Fe ₁ -HNC-500-850 | 0.842 | 0.93 | <i>Adv. Mater.</i> 2020 , 32, 1906905. |
| Fe ₃ C-Co/NC | 0.830 | 0.94 | <i>Adv. Funct. Mater.</i> 2019 , 29, 1901949 |

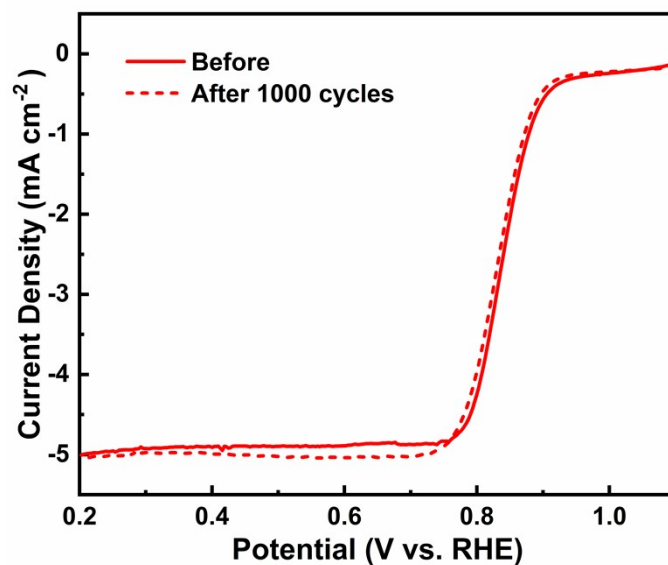


Figure S5. LSV curves of ORR obtained before and after CV tests of 2000 cycles for Fe_xCo_y@N-C-0.3.

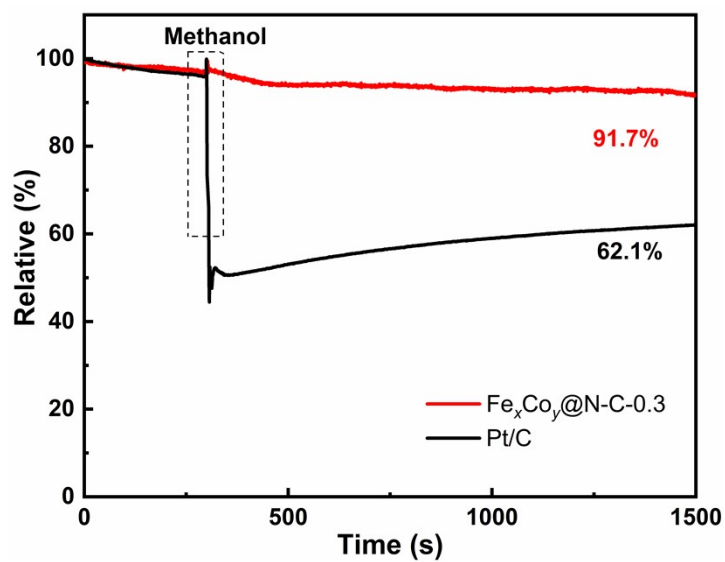


Figure S6. Methanol crossover tolerance test of Fe_xCo_y@N-C-0.3 and Pt/C.

Table S3. Comparison of the OER performance of as-prepared catalysts.

| Catalyst | $E_{j=10}$ (V vs. RHE) | The Tafel slope (mV dec⁻¹) |
|---|--|--|
| Fe _x Co _y @N-C-0.1 | 1.597 | 119.1 |
| Fe_xCo_y@N-C-0.3 | 1.528 | 87.7 |
| Fe _x Co _y @N-C-0.5 | 1.645 | 150.0 |
| Fe@N-C | 1.661 | 169.3 |
| Co@N-C | 1.637 (fast decay) | 147.6 |
| RuO ₂ | 1.607 | 138.8 |

Table S4. Comparison of OER performance (vs. RHE) of Fe_xCo_y@N-C-0.3 with recently reported M-N-C catalysts in alkaline solution.

| Catalyst | $E_{j=10}$ (V) | Tafel slope (mV dec ⁻¹) | Ref. |
|---|----------------|-------------------------------------|--|
| Fe_xCo_y@N-C-0.3 | 1.528 | 87.7 | This work |
| Fe ₈ Co _{0.2} -NC-800 | 1.630 | 89.1 | <i>Nano-Micro Lett.</i> 2023 , 15, 26. |
| Co@C-CoNC | 1.638 | 73.0 | <i>Nano-Micro Lett.</i> 2023 , 15, 48. |
| NP-Co _{S_A} NC | 1.550 | / | <i>Energy Storage Materials</i> 2023 , 56, 165–173. |
| CoNi-CoN ₄ -HPC-900 | 1.700 | 153.0 | <i>Nano Energy</i> 2022 , 99, 107325. |
| CoNP@FeNC-0.05 | 1.630 | 146.0 | <i>Nano-Micro Lett.</i> 2022 , 14, 162 |
| Co@N-HPC-700 | 1.710 | 168.5 | <i>Chem. Eng. J.</i> 2022 , 433, 134469. |
| Fe ₃ C-Co/NC | 1.570 | 49.0 | <i>Adv. Funct. Mater.</i> 2019 , 29, 1901949. |

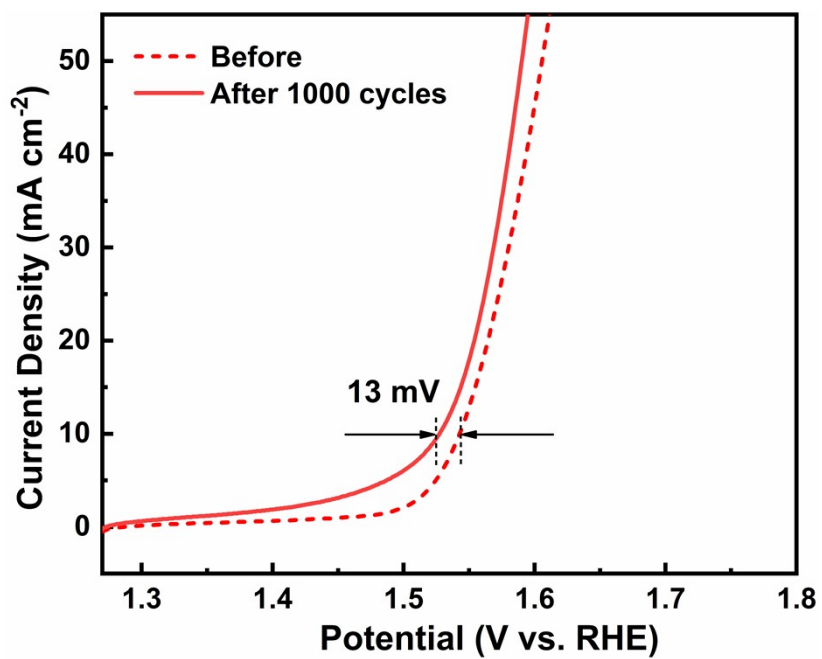


Figure S7. LSV curves of OER obtained before and after CV tests of 2000 cycles for Fe_xCo_y@N-C-0.3.

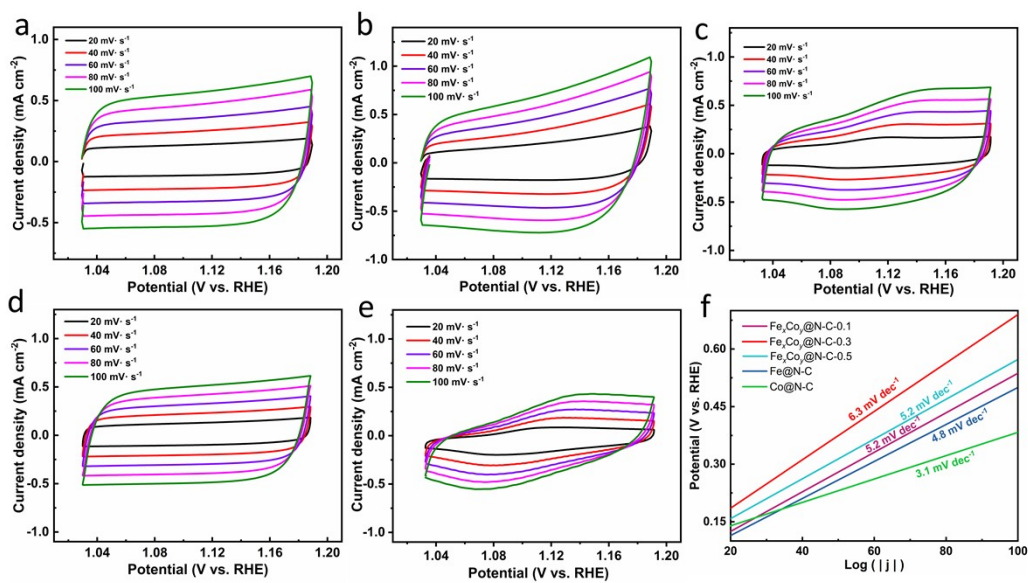


Figure S8. The CV tests at different scan rates of (a) $\text{Fe}_x\text{Co}_y\text{@N-C-0.1}$, (b) $\text{Fe}_x\text{Co}_y\text{@N-C-0.3}$, (c) $\text{Fe}_x\text{Co}_y\text{@N-C-0.5}$, (d) Fe@N-C , (e) Co@N-C-0.5 , and (f) the corresponding C_{dl} value.

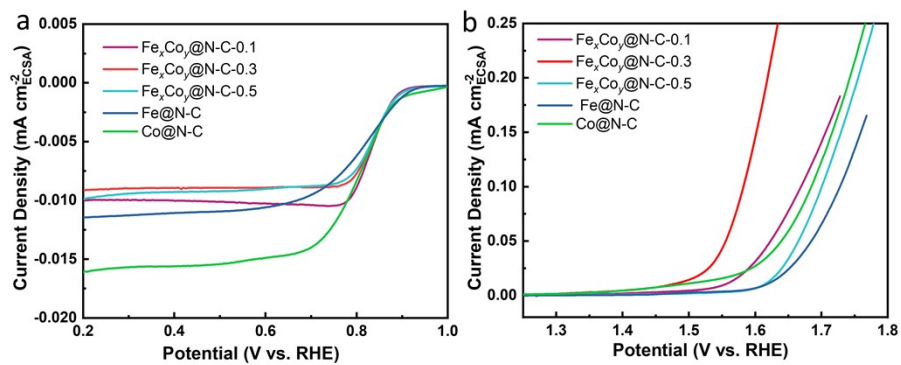


Figure S9. The specific activity based on ECSA for (a) OER and (b) HER.

Table S5. Comparison of the reversible potential difference (ΔE) (vs. RHE) of $\text{Fe}_x\text{Co}_y\text{@N-C-0.3}$ with recently reported M-N-C catalysts in alkaline solution.

| Catalyst | <i>ORR</i> | <i>OER</i> | ΔE | Ref. |
|--|---------------|----------------|--------------|--|
| | $E_{1/2}$ (V) | $E_{j=10}$ (V) | (V) | |
| $\text{Fe}_x\text{Co}_y\text{@N-C-0.3}$ | 0.842 | 1.528 | 0.686 | This work |
| $\text{Fe}_8\text{Co}_{0.2}\text{-NC-800}$ | 0.820 | 1.630 | 0.810 | <i>Nano-Micro Lett.</i> 2023 , 15, 26. |
| NP- Co_sANC | 0.860 | 1.550 | 0.790 | <i>Energy Storage Materials</i> 2023 , 56, 165– 173. |
| CoFe@NC/KB-800 | 0.845 | 1.615 | 0.770 | <i>Chem. Eng. J.</i> 2022 , 427, 131614. |
| $\text{CoNi-CoN}_4\text{-HPC-900}$ | 0.820 | 1.700 | 0.880 | <i>Nano Energy</i> 2022 , 99, 107325. |
| CoNP@FeNC-0.05 | 0.850 | 1.630 | 0.780 | <i>Nano-Micro Lett.</i> 2022 , 14, 162. |
| Co/CoFe@NC | 0.840 | 1.540 | 0.700 | <i>Nano-Micro Lett.</i> 2021 , 13, 126. |
| FeCo/N-HCSs | 0.791 | 1.522 | 0.731 | <i>Chem. Eng. J.</i> 2021 , 407, 127961. |
| $\text{Fe}_3\text{C-Co/NC}$ | 0.830 | 1.570 | 0.740 | <i>Adv. Funct. Mater.</i> 2019 , 29, 1901949 |

Table S6. Performances of recently reported aqueous ZABs based on M-N-C catalysts.

| Catalyst | OCP(V) | Peak power density (mW cm ⁻²) | The voltage gap (V) | Stability | Ref. |
|--|-------------|---|---------------------|--------------------------------------|---|
| Fe_xCo_y@N-C-0.3 | 1.45 | 191.00 | 0.73 | 345 h at 5 mA cm⁻² | This work |
| Fe ₈ Co _{0.2} -NC-800 | ~1.43 | 124.90 | / | 311 h at 5 mA cm ⁻² | <i>Nano-Micro Lett.</i> 2023 , 15, 26. |
| Co@C-CoNC | 1.53 | 162.8 | ~0.85 | 100 h at 2 mA cm ⁻² | <i>Nano-Micro Lett.</i> 2023 , 15, 48. |
| NP-Co _S A _N C | 1.42 | 158.10 | 0.88 | 80 h at 10 mA cm ⁻² | <i>Energy Storage Materials</i> 2023 , 56, 165–173 |
| FeCo-DACs/NC | 1.50 | 175.00 | ~0.91 | 240 h at 10 mA cm ⁻² | <i>Adv. Mater.</i> 2022 , 34, 2107421. |
| Co/ZnCo ₂ O ₄ @NC-CNTs | 1.47 | 305.00 | 0.92 | 103 h at 20 mA cm ⁻² | <i>Nano Energy</i> 2021 , 82, 105710. |
| Co/CoFe@NC | 1.49 | 146.60 | 0.74 | ~360 h at 20 mA cm ⁻² | <i>Nano-Micro Lett.</i> 2021 , 13, 126. |
| CoNC-NB2 | 1.50 | 246.00 | ~1.00 | 140 h at 2 mA cm ⁻² | <i>Small</i> 2020 , 16, 2001171. |
| H-Co@FeCo/N/C | 1.45 | 125.20 | 1.00 | 200 h at 2 mA cm ⁻² | <i>Appl. Catal. B Environ.</i> 2020 , 278, 119259. |
| CoNi-SAs/NC | 1.45 | 101.40 | 0.82 | ~32 h at 5 mA cm ⁻² | <i>Adv. Mater.</i> 2019 , 31, 1905622. |
| Fe/Co-N/S-Cs | ~1.40 | 102.63 | 0.69 | ~30 h at 5 mA cm ⁻² | <i>Appl. Catal. B Environ.</i> 2019 , 241, 95-103. |

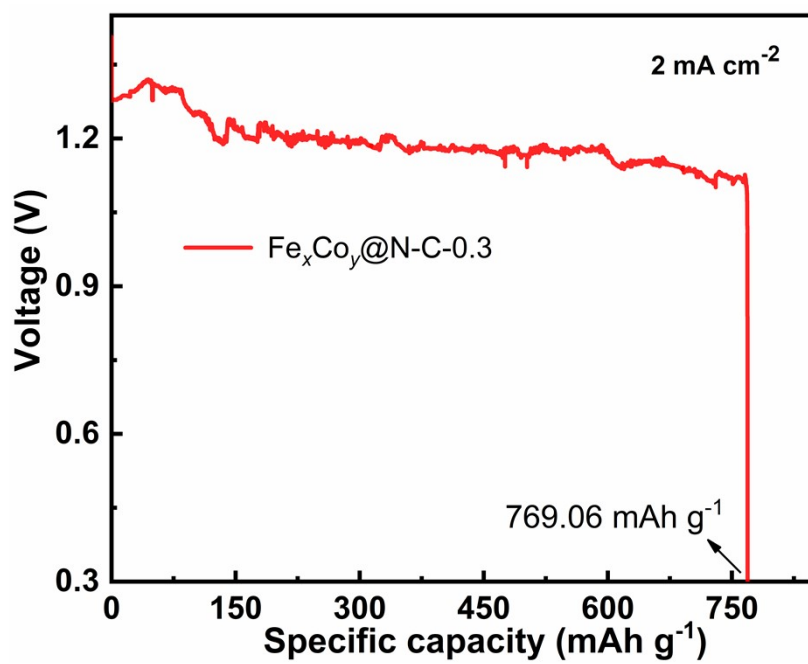


Figure S10. The specific capacity curve of the flexible ZABs based on $\text{Fe}_x\text{Co}_y@N\text{-C-0.3}$.

Table S7. Performances of recently reported flexible ZABs based on M-N-C catalysts.

| Catalyst | OCP (V) | Stability | Ref. |
|--|---------|--------------------------------|--|
| $\text{Fe}_x\text{Co}_y\text{@N-C-0.3}$ | 1.40 | 50 h at 5 mA cm ⁻² | This work |
| $\text{Fe}_8\text{Co}_{0.2}\text{-NC-800}$ | ~1.39 | / | <i>Nano-Micro Lett.</i> 2023 , 15, 26. <i>Energy Storage</i> |
| NP-Co _S A _N C | 1.32 | 5 h at 2 mA cm ⁻² | <i>Materials</i> 2023 , 56, 165–173. |
| CoNi-CoN ₄ -HPC-900 | 1.50 | ~27 h at 5 mA cm ⁻² | <i>Nano Energy</i> , 2022 , 99, 107325. |
| CoFe/N-HCSs | 1.40 | 10 h at 1 mA cm ⁻² | <i>Chem. Eng. J.</i> 2021 , 407, 127961. |
| CoFe@NO-CNT | 1.45 | 56 h at 2 mA cm ⁻² | <i>Electrochimica Acta</i> 2021 , 388, 138587. |
| Co/CoFe@NC | 1.48 | ~92 h at 5 mA cm ⁻² | <i>Nano-Micro Lett.</i> 2021, 13, 126. |
| Co/ZnCo ₂ O ₄ @NC-CNTs | 1.30 | ~20 h at 5 mA cm ⁻² | <i>Nano Energy</i> 2021 , 82, 105710. |
| CoFe/N-HCSs | 1.40 | 10 h at 1 mA cm ⁻² | <i>Chem. Eng. J.</i> 2021 , 407, 127961 |
| Co-NCNT | 1.42 | 30 h at 2 mA cm ⁻² | <i>Carbon Energy</i> 2020 , 2, 461-471. |