

## Supporting Information

# 2-D Transition Metal Trichalophosphogenide FePS<sub>3</sub> Against Multi-Drug Resistant Microbial Infections

SHREEHARI KODAKKAT<sup>1</sup>, PIERRE H.A. VALLIANT,<sup>1</sup> SERENA CH'NG,<sup>1</sup> Z.L. SHAW,<sup>2</sup> MIYAH NAIM AWAD,<sup>1</sup> BILLY J. MURDOCH,<sup>1</sup> ANDREW J. CHRISTOFFERSON,<sup>1</sup> SAFFRON J. BRYANT,<sup>1,\*</sup> SUMEET WALIA,<sup>1,\*</sup> and AARON ELBOURNE<sup>1,\*</sup>


\*Corresponding Authors

<sup>1</sup>School of Science, RMIT University, Melbourne VIC 3001, Australia.


<sup>2</sup>School of Engineering, RMIT University, Melbourne VIC 3001, Australia.

**Key words:** antibacterial, antimicrobial, bacteria, fungi, iron phosphorus trisulfide


## Supplementary Material

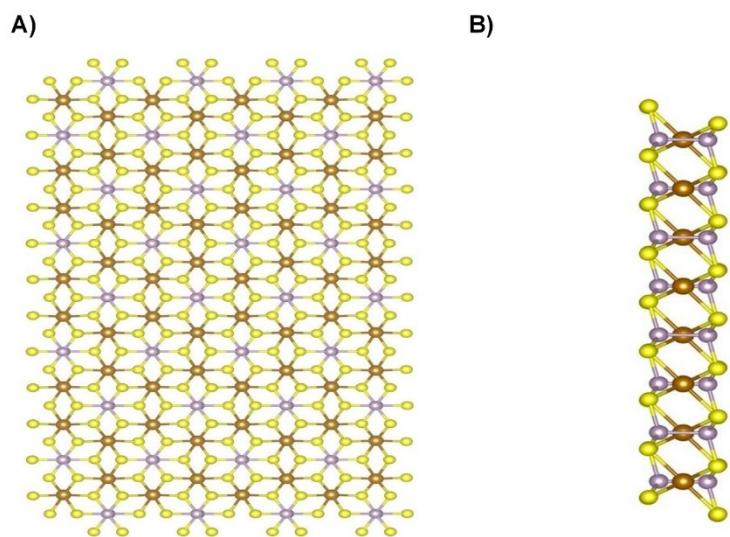


**Figure S1.** 3-D Structure of mechanically- exfoliated FePS<sub>3</sub> nanosheet (Monolayer)

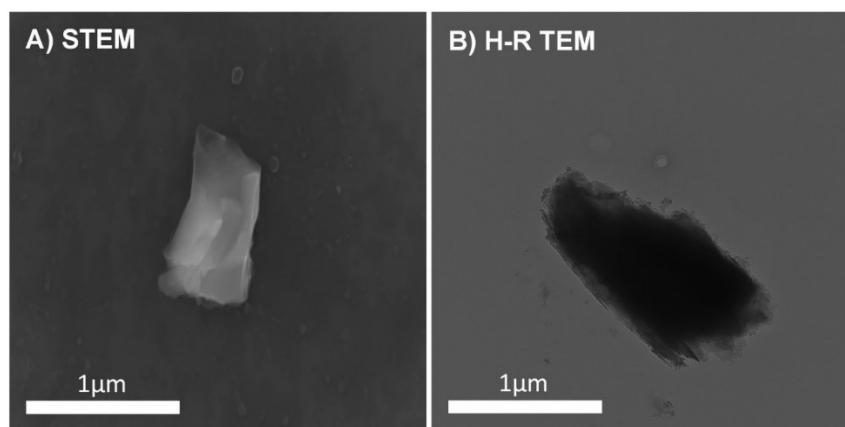


**Figure S2.** Additional Characterization of flakes A) STEM image, B) H-R TEM image

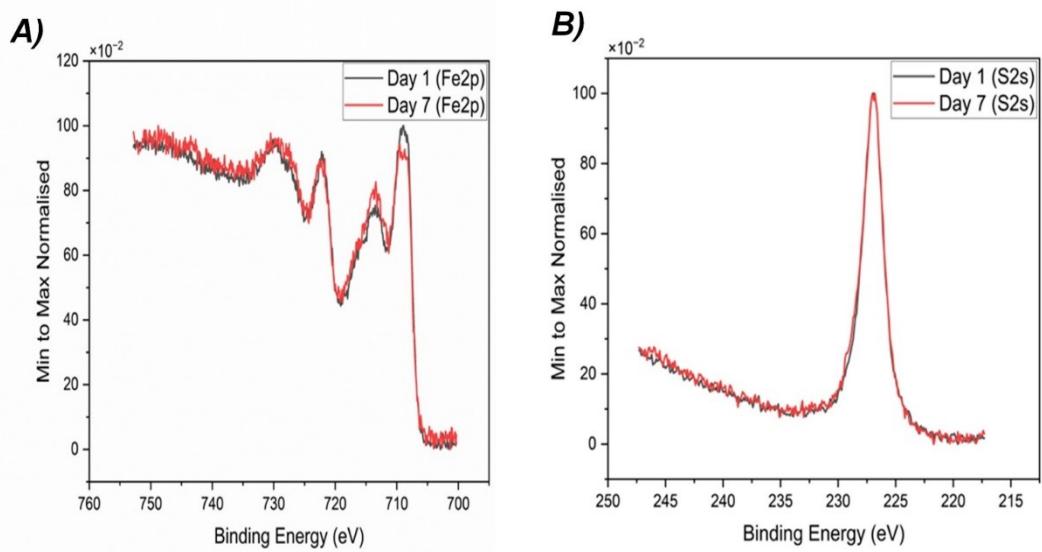

**Figure S3.** XPS analysis of the exfoliated flakes showing peaks in the (A) iron and (B) sulphur components.

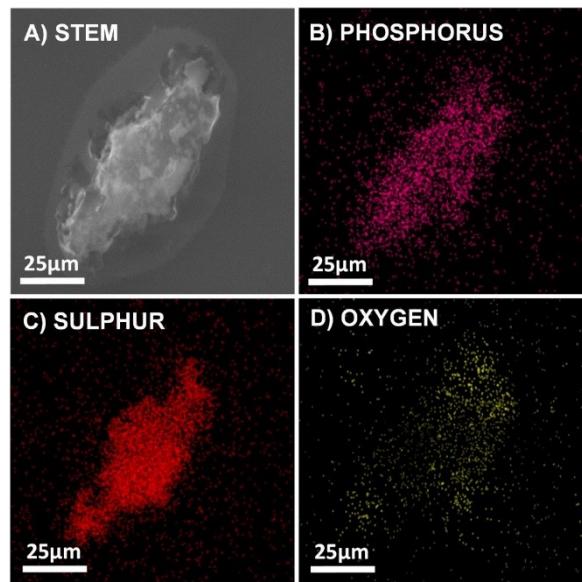


**Figure S4.** Degradation of FePS<sub>3</sub> nanoflakes. A) STEM image of a degrading FePS<sub>3</sub> nanoflake after 24 hours under ambient conditions. Corresponding EDS images showing B) phosphorus, C) sulphur, and D) oxygen components.

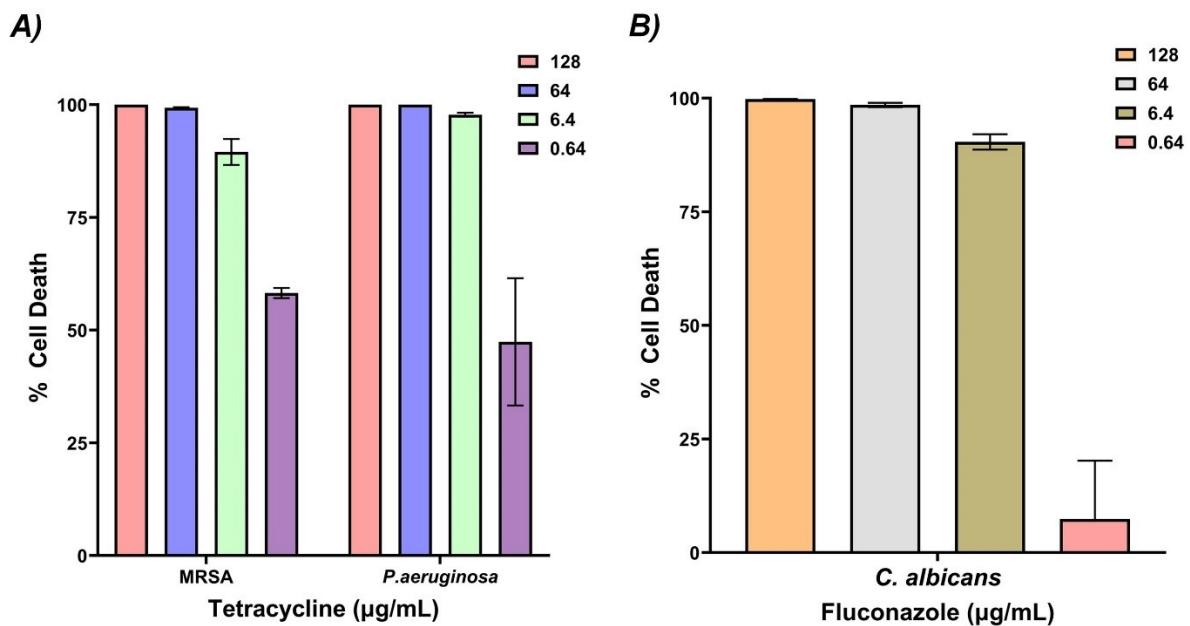


**Figure S5:** Antimicrobial efficacy of positive controls. (A) Tetracycline was used as a positive control for bacterial strains (MRSA and *P. aeruginosa*) and (B) Fluconazole for *Candida albicans*. The concentrations used for both positive controls are in a range of 0.64- 128  $\mu\text{g/mL}$ . Values are mean  $\pm$  SEM. n = 3.


***C. albicans***

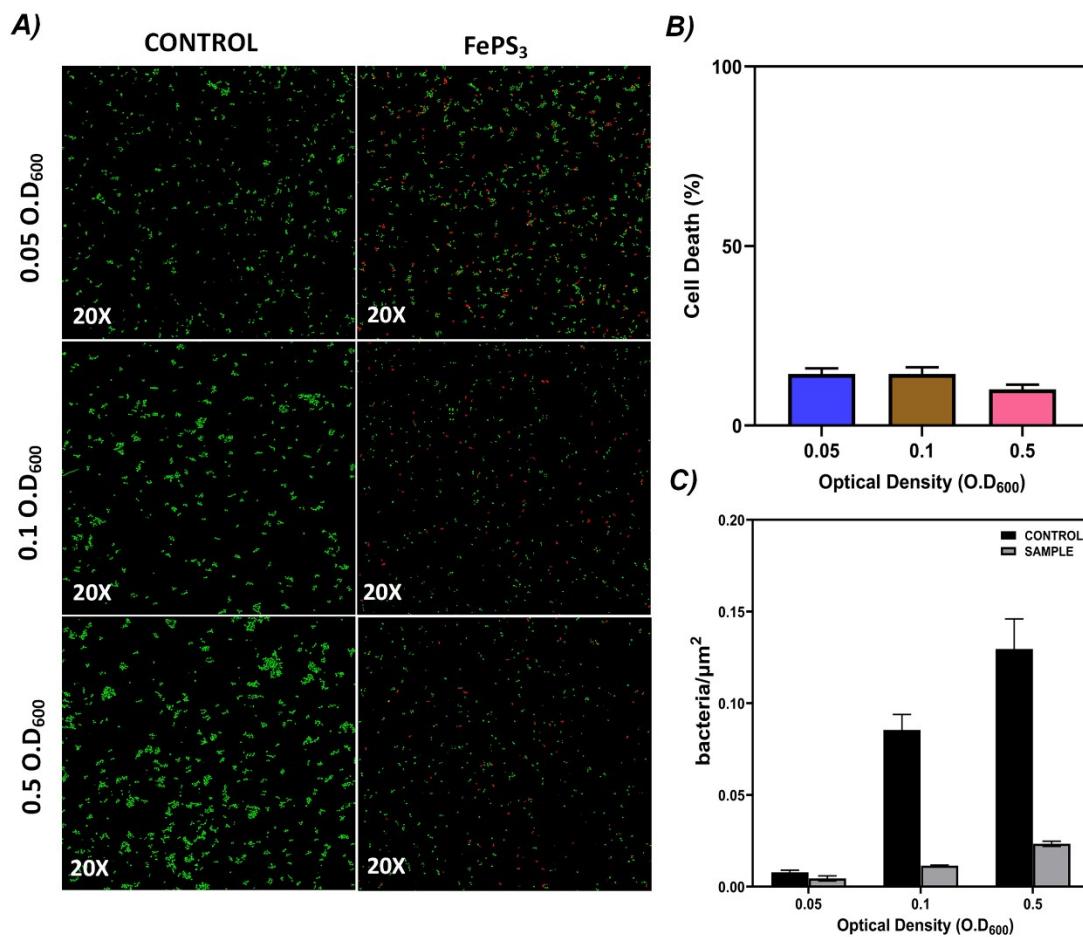

**Figure S6.** Antimicrobial properties of  $\text{FePS}_3$  nanoflakes against a series of fungal population densities. (A) CLSM images of control and treated *C. albicans*. (B) Relative quantification of cell death in fungi.

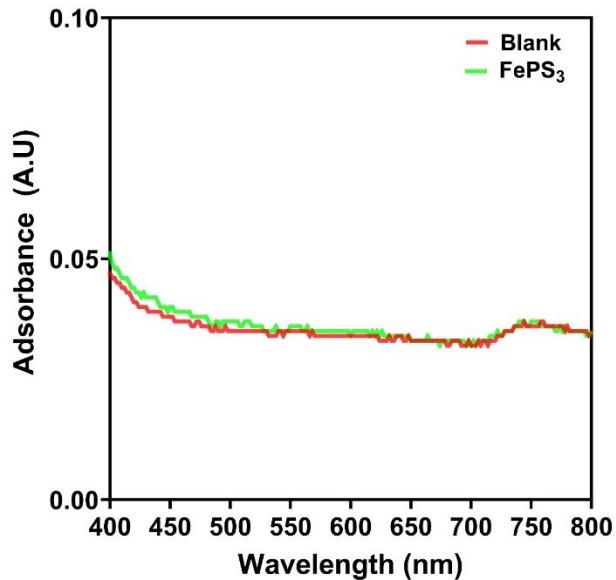

**Figure S7.** UV-Vis adsorbance spectra of blank (in red) and FePS<sub>3</sub> treated samples (in green).

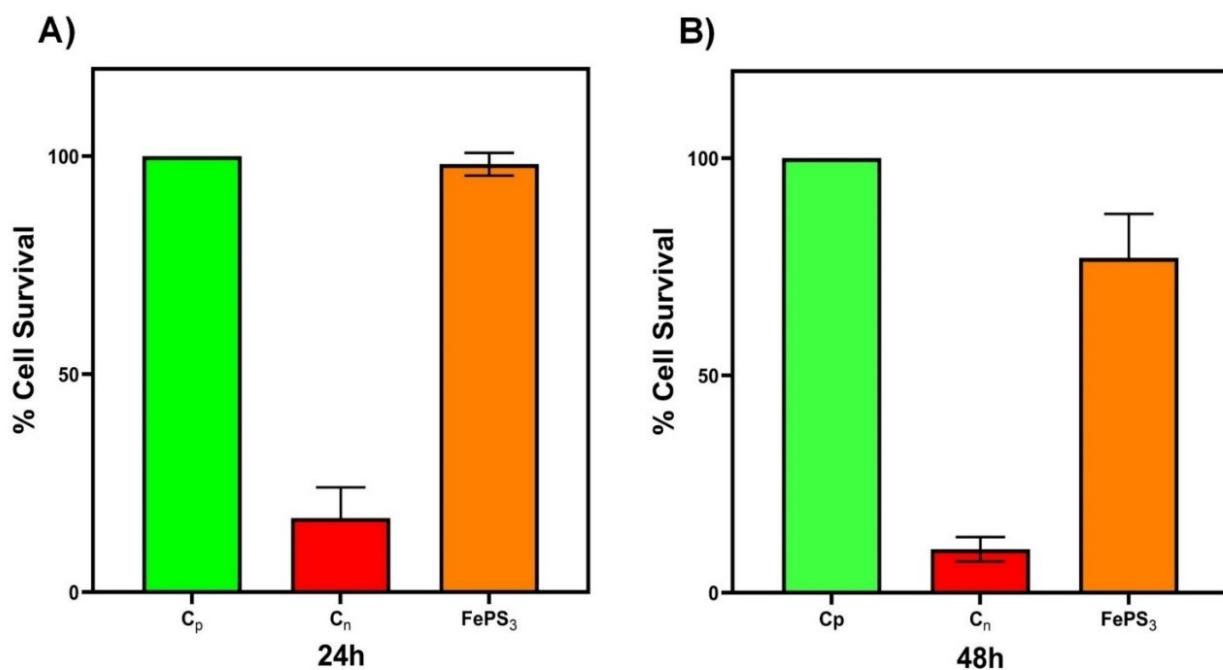

**Figure S8.** Hemolysis assay of FePS<sub>3</sub> nanoflakes against red blood cells. (A) 24 h and (B) 48 h. Cp corresponds to the positive control (C<sub>p</sub>), and C<sub>n</sub> negative control (treated with 100% ethanol).

**Table S1. Table is recreated from Shaw *et al.*, 2021<sup>1</sup>.** Comparative antimicrobial activity of commonly investigated nanomaterials. Abbreviations: BP: black phosphorus, NMP: N-methyl-2-pyrrolidone, DMPI: N,N'-dimethylpropyleneurea, PPMS: 4-pyridonemethylstyrene, NPs: nano-particles, NB: Not bactericidal, N/A: Not applicable, NR: Not reported. Material 1 highlighted in blue is that of this study.

Materials	Sizes/ Thickness	Concentration	Activated	Microbes Tested		Mammalian Testing		Treatment Parameters			
				Bacteria	Fungi	Cytotoxicity	Bactericidal Activity	Bacterial Treatment Times	Fungicidal Activity	Bactericidal Treatment time	
Mechanically Exfoliated FePS <sub>3</sub>	Size: 2-4μm Thickness: 65nm	816.7 ng/cm <sup>2</sup>	No	MRSA, <i>P.aeruginosa</i>	<i>C.albicans</i>	No	99.99% (MRSA) and 99.9% ( <i>P.aeruginosa</i> )	4 hours	50% ( <i>C.albicans</i> )	4 hours	
Mechanically Exfoliated BP	Size: 500 nm - 5 μm Thickness: 15 – 90 nm	~900 ng/cm <sup>2</sup>	No	<i>E. coli</i> , <i>P. aeruginosa</i> , MRSA, <i>S. typhimurium</i> , and <i>B. cereus</i>	<i>C. albicans</i> , <i>C. auris</i> and sensitive, fluconazole-resistant, and Amphotericin B-resistant <i>C. neoformans</i> .	No	96.3% ( <i>E.coli</i> ) and 96.2% ( <i>P. aeruginosa</i> )	2 hours	99.92% ( <i>C. albicans</i> ) and 99.3% ( <i>C. neoformans</i> {F <sup>R</sup> })	2 hours	
NMP - BP with Ti-SA <sub>4</sub> <sup>2</sup>	Size: 220 nm Thickness: 5 nm	50 μg/mL	No	<i>E. coli</i> & <i>S. aureus</i>	No	NR	99.2% ( <i>E. coli</i> ), 94.6 % ( <i>S. aureus</i> ).	3 hr	NR	NR	
DMPU - BP <sup>3</sup>	Size: 0.1 - 4 μm. Thickness: 2 - 15.4 nm	160 μg/mL	Yes, NIR irradiation at 808 nm.	<i>E. coli</i> & <i>S. aureus</i>	No	NR	99.2%	3 - 10 min	NR	NR	

Ag and BP nanosheets <sup>4</sup>	AgNPs: 30 nm BP: 220 nm Thickness: 4 nm	25 - 40 µg/mL	Yes; NIR irradiation at 808 nm.	MRSA	No	No	93%.	5 min	NR	NR
DCM - BP with PPMS <sup>5</sup>	Size: microns Thickness: 4.2 - 4.5 nm	100 µg/ml	Yes; irradiation at 660 nm	<i>E. coli</i> & <i>S. aureus</i>	No	No	99.3% & 99.2% ( <i>E. coli</i> ), 76.5% & 69.5% ( <i>S.aureus</i> ).	10 min	NR	NR
Millipore water - BP	Size: 215.8 nm Thickness: 1.6 nm	50- 100 µg/mL.	No	<i>E. coli</i> & <i>B. subtilis</i>	No	NR	91.65% & 99.69%	6 - 12 hr	NR	NR
Au-BP Nanosheets <sup>6</sup>	Size: >100 nm Thickness: 2 nm	<10 µg/mL	No	<i>E. coli</i>	No	NR	94.7%	8 hr	NR	NR
BP-TiO <sub>2</sub> <sup>7</sup>	NR	25 µg/mL	Yes; UV-vis	<i>E. coli</i> & <i>S. aureus</i>	No	NR	NR	70 min	NR	NR
MoS <sub>2</sub> Composites <sup>8, 9</sup>	Size: NR Thickness: 2.2 nm	≤1 mg/mL	Yes, NIR <sup>8</sup>	<i>E. coli</i> & <i>S. aureus</i>	No	Concentration & system dependent <sup>10, 11</sup>	100%	≤6 hr	NR	NR
Ag NPs <sup>12</sup>	Size: 4 - 24 nm	50 µg/mL	No	<i>E. coli</i>	Yes <sup>13-16</sup>	Yes; shape & concentration dependent <sup>17</sup>	100%	24 hr	Varying degrees. <sup>15, 18</sup>	NR
Au NPs <sup>19</sup>	Size: 10 - 200 nm	Widely Variant	No	Controversial <sup>19</sup>	Yes; <sup>20, 21</sup> controversial	Dose & size dependent <sup>24</sup>	NB	N/A	MIC: 4 - 48 µg/mL	NR
ZnO NPs <sup>25, 26</sup>	Size: 50 - 250 nm	0.25 g/L	Yes, UV-vis <sup>25, 26</sup>	<i>E. coli</i> & <i>S. aureus</i>	Numerous Species <sup>27-29</sup>	Yes <sup>30-32</sup>	Conditional, but >99%	2 hr	Yes <sup>28, 29, 33</sup>	NR

Graphene oxide (pure & reduced) <sup>34</sup>	Size: ~0.31 µm Size: ~2.75 µm	80 µg/mL	No	<i>E. coli</i>	Yes; <sup>35</sup> enhanced with NIR <sup>36</sup>	Morphology, chemistry, sys dependent <sup>37, 38</sup>	Pure: 90% Reduced: 80%	2 hr	IC <sub>50</sub> : 50 – 100 µg/mL <sup>35</sup>	NR
Graphene oxide <sup>39</sup>	Size: 5 - 20 µm Thickness: 1.2 nm	200 µg/mL	No	None for pure graphene oxide	NR	NR	0%	N/A	NR	NR
TiO <sub>2</sub> NPs <sup>40</sup>	Size: 79 nm	1200 µM	UV-visible Light	<i>E. coli</i>	Yes <sup>41</sup> , surface additive <sup>42, 43</sup>	Yes, concentration- & time-dependent manner. <sup>44</sup>	75% reduction	N/A	Yes <sup>41, 45</sup>	NR
Cu-TiO <sub>2</sub> NPs <sup>46</sup>	Size: 15-50 nm	1 mg/mL	UV-vis	<i>E. coli</i>	NR	NR	100% reduction	N/A	NR	NR
Au nanostar <sup>47</sup>	Size: 50 – 100 nm	Monolayer of nanostar on glass	NIR laser	<i>S. aureus</i>	NR	NR	99%	30 min	NR	NR
Au nanocross <sup>48</sup>	Size: ~100 nm	0.2 mg/mL	NIR laser	<i>P. aeruginosa</i>	NR	NR	99%	5 min	NR	NR

## References

1. Z. L. Shaw, S. Kuriakose, S. Cheeseman, E. L. H. Mayes, A. Murali, Z. Y. Oo, T. Ahmed, N. Tran, K. Boyce, J. Chapman, C. F. McConville, R. J. Crawford, P. D. Taylor, A. J. Christofferson, V. K. Truong, M. J. S. Spencer, A. Elbourne and S. Walia, *ACS Applied Materials & Interfaces*, 2021, **13**, 17340-17352.
2. Z. Li, L. Wu, H. Wang, W. Zhou, H. Liu, H. Cui, P. Li, P. K. Chu and X.-F. Yu, *ACS Applied Nano Materials*, 2019, **2**, 1202-1209.
3. Z. Sun, Y. Zhang, H. Yu, C. Yan, Y. Liu, S. Hong, H. Tao, A. W. Robertson, Z. Wang and A. A. H. Pádua, *Nanoscale*, 2018, **10**, 12543-12553.
4. J. Ouyang, R.-Y. Liu, W. Chen, Z. Liu, Q. Xu, K. Zeng, L. Deng, L. Shen and Y.-N. Liu, *Journal of Materials Chemistry B*, 2018, **6**, 6302-6310.
5. L. Tan, J. Li, X. Liu, Z. Cui, X. Yang, K. W. K. Yeung, H. Pan, Y. Zheng, X. Wang and S. Wu, *Small*, 2018, **14**, 1703197.
6. Q. Wu, M. Liang, S. Zhang, X. Liu and F. Wang, *Nanoscale*, 2018, **10**, 10428-10435.
7. H. Uk Lee, S. C. Lee, J. Won, B.-C. Son, S. Choi, Y. Kim, S. Y. Park, H.-S. Kim, Y.-C. Lee and J. Lee, *Scientific Reports*, 2015, **5**, 8691.
8. W. Zhang, S. Shi, Y. Wang, S. Yu, W. Zhu, X. Zhang, D. Zhang, B. Yang, X. Wang and J. Wang, *Nanoscale*, 2016, **8**, 11642-11648.
9. T. I. Kim, B. Kwon, J. Yoon, I.-J. Park, G. S. Bang, Y. Park, Y.-S. Seo and S.-Y. Choi, *ACS Applied Materials & Interfaces*, 2017, **9**, 7908-7917.
10. W. Z. Teo, E. L. K. Chng, Z. Sofer and M. Pumera, *Chemistry – A European Journal*, 2014, **20**, 9627-9632.
11. X. Wang, N. D. Mansukhani, L. M. Guiney, Z. Ji, C. H. Chang, M. Wang, Y.-P. Liao, T.-B. Song, B. Sun, R. Li, T. Xia, M. C. Hersam and A. E. Nel, *Small*, 2015, **11**, 5079-5087.
12. I. Sondi and B. Salopek-Sondi, *Journal of colloid and interface science*, 2004, **275**, 177-182.
13. S. W. Kim, J. H. Jung, K. Lamsal, Y. S. Kim, J. S. Min and Y. S. Lee, *Mycobiology*, 2012, **40**, 53-58.
14. E. J. J. Mallmann, F. A. Cunha, B. N. M. F. Castro, A. M. Maciel, E. A. Menezes and P. B. A. Fechine, *Rev Inst Med Trop Sao Paulo*, 2015, **57**, 165-167.
15. A. Panáček, M. Kolář, R. Večeřová, R. Prucek, J. Soukupova, V. Kryštof, P. Hamal, R. Zbořil and L. Kvítek, *Biomaterials*, 2009, **30**, 6333-6340.
16. J. J. Artunduaga Bonilla, D. J. Paredes Guerrero, C. I. Sánchez Suárez, C. C. Ortiz López and R. G. Torres Sáez, *World Journal of Microbiology and Biotechnology*, 2015, **31**, 1801-1809.
17. T. Zhang, L. Wang, Q. Chen and C. Chen, *Yonsei Med J*, 2014, **55**, 283-291.
18. Z.-K. Xia, Q.-H. Ma, S.-Y. Li, D.-Q. Zhang, L. Cong, Y.-L. Tian and R.-Y. Yang, *Journal of Microbiology, Immunology and Infection*, 2016, **49**, 182-188.
19. Y. Zhang, T. P. Shareena Dasari, H. Deng and H. Yu, *Journal of Environmental Science and Health, Part C*, 2015, **33**, 286-327.
20. T. Ahmad, I. A. Wani, I. H. Lone, A. Ganguly, N. Manzoor, A. Ahmad, J. Ahmed and A. S. Al-Shihri, *Materials Research Bulletin*, 2013, **48**, 12-20.
21. C. E. Peña-González, E. Pedziwiatr-Werbicka, T. Martín-Pérez, E. M. Szewczyk, J. L. Copa-Patiño, J. Soliveri, J. Pérez-Serrano, R. Gómez, M. Bryszewska, J. Sánchez-Nieves and F. J. de la Mata, *International Journal of Pharmaceutics*, 2017, **528**, 55-61.
22. P. Falagan-Lotsch, E. M. Grzincic and C. J. Murphy, *Proceedings of the National Academy of Sciences*, 2016, **113**, 13318-13323.
23. J.-Y. Wang, J. Chen, J. Yang, H. Wang, X. Shen, Y.-M. Sun, M. Guo and X.-D. Zhang, *International journal of nanomedicine*, 2016, **11**, 3475.
24. Y. Pan, S. Neuss, A. Leifert, M. Fischler, F. Wen, U. Simon, G. Schmid, W. Brandau and W. Jahnens-Dechent, *Small*, 2007, **3**, 1941-1949.
25. L. Zhang, Y. Jiang, Y. Ding, M. Povey and D. York, *Journal of Nanoparticle Research*, 2007, **9**, 479-489.
26. E. Ozkan, E. Allan and I. P. Parkin, *ACS Omega*, 2018, **3**, 3190-3199.

27. P. A. Arciniegas-Grijalba, M. C. Patiño-Portela, L. P. Mosquera-Sánchez, J. A. Guerrero-Vargas and J. E. Rodríguez-Páez, *Applied Nanoscience*, 2017, **7**, 225-241.
28. M. A. Gondal, A. J. Alzahrani, M. A. Randhawa and M. N. Siddiqui, *Journal of Environmental Science and Health, Part A*, 2012, **47**, 1413-1418.
29. A. Lipovsky, Y. Nitzan, A. Gedanken and R. Lubart, *Nanotechnology*, 2011, **22**, 105101.
30. V. Sharma, R. K. Shukla, N. Saxena, D. Parmar, M. Das and A. Dhawan, *Toxicology letters*, 2009, **185**, 211-218.
31. W. Song, J. Zhang, J. Guo, J. Zhang, F. Ding, L. Li and Z. Sun, *Toxicology letters*, 2010, **199**, 389-397.
32. V. Sharma, D. Anderson and A. Dhawan, *Apoptosis*, 2012, **17**, 852-870.
33. P. Arciniegas-Grijalba, M. Patiño-Portela, L. Mosquera-Sánchez, J. Guerrero-Vargas and J. Rodríguez-Páez, *Applied Nanoscience*, 2017, **7**, 225-241.
34. S. Liu, T. H. Zeng, M. Hofmann, E. Burcombe, J. Wei, R. Jiang, J. Kong and Y. Chen, *ACS nano*, 2011, **5**, 6971-6980.
35. M. Sawangphruk, P. Srimuk, P. Chiochan, T. Sangsri and P. Siwayaprahm, *Carbon*, 2012, **50**, 5156-5161.
36. M. Shahnaz Khan, H. N. Abdelhamid and H.-F. Wu, *Colloids and Surfaces B: Biointerfaces*, 2015, **127**, 281-291.
37. S. Das, S. Singh, V. Singh, D. Joung, J. M. Dowding, D. Reid, J. Anderson, L. Zhai, S. I. Khondaker and W. T. Self, *Particle & Particle Systems Characterization*, 2013, **30**, 148-157.
38. K.-H. Liao, Y.-S. Lin, C. W. Macosko and C. L. Haynes, *ACS Applied Materials & Interfaces*, 2011, **3**, 2607-2615.
39. I. Barbolina, C. R. Woods, N. Lozano, K. Kostarelos, K. S. Novoselov and I. S. Roberts, *2D Materials*, 2016, **3**, 025025.
40. L. n. Brunet, D. Y. Lyon, E. M. Hotze, P. J. Alvarez and M. R. Wiesner, *Environmental science & technology*, 2009, **43**, 4355-4360.
41. F. Haghghi, S. Roudbar Mohammadi, P. Mohammadi, S. Hosseinkhani and R. Shipour, *Infection, Epidemiology and Microbiology*, 2013, **1**, 33-38.
42. S. Darbari, Y. Abdi, F. Haghghi, S. Mohajerzadeh and N. Haghghi, *Journal of Physics D: Applied Physics*, 2011, **44**, 245401.
43. N. Haghghi, Y. Abdi and F. Haghghi, *Applied Surface Science*, 2011, **257**, 10096-10100.
44. I.-S. Kim, M. Baek and S.-J. Choi, *Journal of Nanoscience and Nanotechnology*, 2010, **10**, 3453-3458.
45. N. S. Ahmad, N. Abdullah and F. M. Yasin, *BioResources*, 2019, **14**, 8866-8878.
46. M. Y. Guo, F. Liu, Y. H. Leung, Y. He, A. M. C. Ng, A. B. Djurišić, H. Li, K. Shih and W. K. Chan, *The Journal of Physical Chemistry C*, 2017, **121**, 24060-24068.
47. P. Pallavicini, A. Dona, A. Taglietti, P. Minzioni, M. Patrini, G. Dacarro, G. Chirico, L. Sironi, N. Bloise and L. Visai, *Chemical Communications*, 2014, **50**, 1969-1971.
48. C. P. Teng, T. Zhou, E. Ye, S. Liu, L. D. Koh, M. Low, X. J. Loh, K. Y. Win, L. Zhang and M. Y. Han, *Advanced healthcare materials*, 2016, **5**, 2122-2130.